

# **RECYCLABILITY EVALUATION PROTOCOL FOR HDPE CONTAINERS**

Standard Laboratory Practice

Version 1.0

Published on 18<sup>th</sup> July 2019

## CONTENTS

1. Introduction and purpose of the Protocol .....	5
2. Scope of the Protocol.....	5
3. Disclaimer.....	6
4. Laboratory Test Methodology .....	6
4.1. Control Selection.....	8
4.2. Pre-treatment.....	8
4.2.1. Grinding .....	8
4.2.2. Air Elutriation.....	9
4.2.3. Washing .....	9
4.2.4. Flotation.....	10
4.2.5. Drying.....	10
4.2.6. Air Elutriation.....	11
5. Extrusion.....	11
5.1. Flake Blends Preparation.....	11
5.2. Flake Blends Composition .....	11
5.3. Pellet Production .....	12
5.3.1. Filtration Test (optional) .....	13
5.3.2. Pellet Properties Evaluation .....	14
6. Conversion.....	15
6.1. Pellet Blends Composition .....	15
6.2. Bottles Production .....	15
6.2.1. Bottle Properties Evaluation.....	16
6.2.2. Tensile properties testing .....	17
6.3. Sheets Production (OPTIONAL) .....	17
6.3.1. Sheet Properties Evaluation .....	18
6.4. Plaques Production (OPTIONAL) .....	19
6.4.1. Plaque Properties Evaluation .....	20
Annex I - Control samples selection .....	21

## **GLOSSARY**

- A.0 100% control container flakes
- A.25 blend 75/25 control/innovation flakes
- A.50 blend 50/50 control/innovation flakes
- ASTM American Society for Testing and Materials
- B.0 bottle with 100% control pellets
- B.25 bottle with 87.5/12.5 control/innovation pellets
- B.50 bottle with 75/25 control/innovation pellets
- C.0 sheet with 100% control pellets
- C.25 sheet with 87.5/12.5 control/innovation pellets
- C.50 sheet with 75/25 control/innovation pellets
- D.0 plaque with 100% pellets
- D.25 plaque with 87.5/12.5 control/innovation pellets
- D.50 plaque with 75/25 control/innovation pellets
- EN European Standard

Innovation: new container, flakes or pellets from new container which has to be tested

- ISO International Organization for Standardization
- MFI Melt Flow Index
- PE HD High Density Polyethylene
- PP Polypropylene
- PVC Poly Vinyl Chloride
- TC Technical Committee
- TGA Thermo Gravimetical Analysis

Note:

RecyClass is an initiative aiming at enhancing and evaluating the recyclability of plastic packaging through a technical perspective. The Plastics Recyclability Evaluation Protocols will promote recyclability by encouraging industry to test new plastic technologies, materials or product before market launch and giving advice and recommendations to the companies. The Recyclability Evaluation Protocols are available for download in the PRE and RecyClass websites. Companies providing plastic packaging concepts are encouraged to use them to self-assess the impact of their solutions on recyclability and highlight potential issues. **However, compliance to a Recyclability Evaluation Protocol is not a replacement for an official assessment and may not be used as a marketing tool. All tests must follow the Evaluation Protocols recommended by the RecyClass Technical Committees and must be conducted by an independent laboratory approved by RecyClass which has no legal affiliation to the applicant.** More information is reported in the *RecyClass Internal Procedures* available in the RecyClass website”

## 1. INTRODUCTION AND PURPOSE OF THE PROTOCOL

The “Recyclability Evaluation Protocol for HDPE containers” referred to in this document as “The Protocol” describes the methodology that must be followed by the Applicant at a laboratory scale in order to determine if a plastic packaging innovation is compatible with the post-consumer HDPE recycling stream. The Protocol targets companies responsible for introducing a packaging product (innovation) into the market. The Applicant shall proceed with the Protocol as established in the Assessment Process for Applicants of Recyclability Evaluation in the “RecyClass<sup>1</sup> Internal Procedures”.

The Protocol analyzes whether an innovation will undergo the necessary pre-treatment, extrusion and conversion steps described in this methodology at a laboratory scale without negatively impacting the recycling process. It aims to guarantee recyclability<sup>2</sup> of plastics packaging while encouraging innovation in the HDPE market. The overall goal is to maintain the protection of packaged goods and their marketing display functions without obstructing the proper functioning of the HDPE recycling process.

This document provides guidance on the tests methodology that shall be followed, including benchmark recommendations to guide the interpretation of the results.

HDPE terminology as it is used in this document, refers to rigid plastic containers predominantly used for packaging liquids, cosmetics and detergents, as well as food contact applications.

## 2. SCOPE OF THE PROTOCOL

The scope of the Protocol covers any innovation introduced to the existing packaging solutions for HDPE. Prior to initiating the evaluation, the Applicant shall review the Design for Recycling Guidelines for natural and colored HDPE containers<sup>3</sup> in order to confirm that the HDPE innovation is compatible with these requirements.

The following packaging solutions and/or innovations are covered by the scope of this Protocol:

1. HDPE resins
2. Barrier materials
3. Mineral fillers and additives that increase the density of the HDPE packaging
4. Non-PE closure systems
5. Non-PE liners, seals and valves
6. Non-PE labels and sleeves

---

<sup>1</sup>RecyClass assesses the recyclability of a plastic packaging providing a ranking from A to F. RecyClass also provides specific indications and recommendations on how to improve packaging design to fit current recycling technologies. More information at <http://www.recyclclass.eu/en/home/>

<sup>2</sup> Recyclability definition according to PRE & APR: Plastics must meet four conditions for a product to be considered recyclable: 1. The product must be made with a plastic that is collected for recycling, has market value and/or is supported by a legislatively mandated program. 2. The product must be sorted and aggregated into defined streams for recycling processes. 3. The product can be processed and reclaimed/recycled with commercial recycling processes. 4. The recycled plastic becomes a raw material that is used in the production of new products.

<sup>3</sup> Design for Recycling Guidelines <https://plasticsrecyclers.eu/downloads>

7. Adhesives
8. Inks

Packaging containing aluminum, metal, foam, degradable plastics, black carbon surface, as well as PVC shall be separately considered by the RecyClass HDPE Technical Committee in order to assess their suitability under the scope of this Protocol.

### **3. DISCLAIMER**

The Protocol is created to represent as accurately as possible how the current HDPE recycling works at an industrial scale. RecyClass HDPE Technical Committee reserves the right for further testing if necessary, to issue an additional opinion on the recyclability of the tested packaging.

Within RecyClass, “easy-to-empty” and “easy-to-access” indexes are important factors when considering the recyclability of a packaging. At the state of the art, at HDPE mechanical recycling facilities washing operation typically uses mild conditions, no detergents nor strong chemicals. Consequently, any organic residue constitutes an impurity for the recycling stream. Anyway, Plastics Recyclers Europe encourages testing to verify that the packaging is “easy-to-empty” and therefore ensures the minimum amount of leftover material at the end of its useful life.


Nonetheless, this factor is beyond the scope of this Protocol and can be assessed with the RecyClass tool.

### **4. LABORATORY TEST METHODOLOGY**

This methodology aims to reproduce the recycling process at a small scale to determine the suitability of an innovation material for the HDPE recycling stream.

See below in Figure 1 a diagram where the flow of the methodology is described.

Figure1: Methodology Diagram

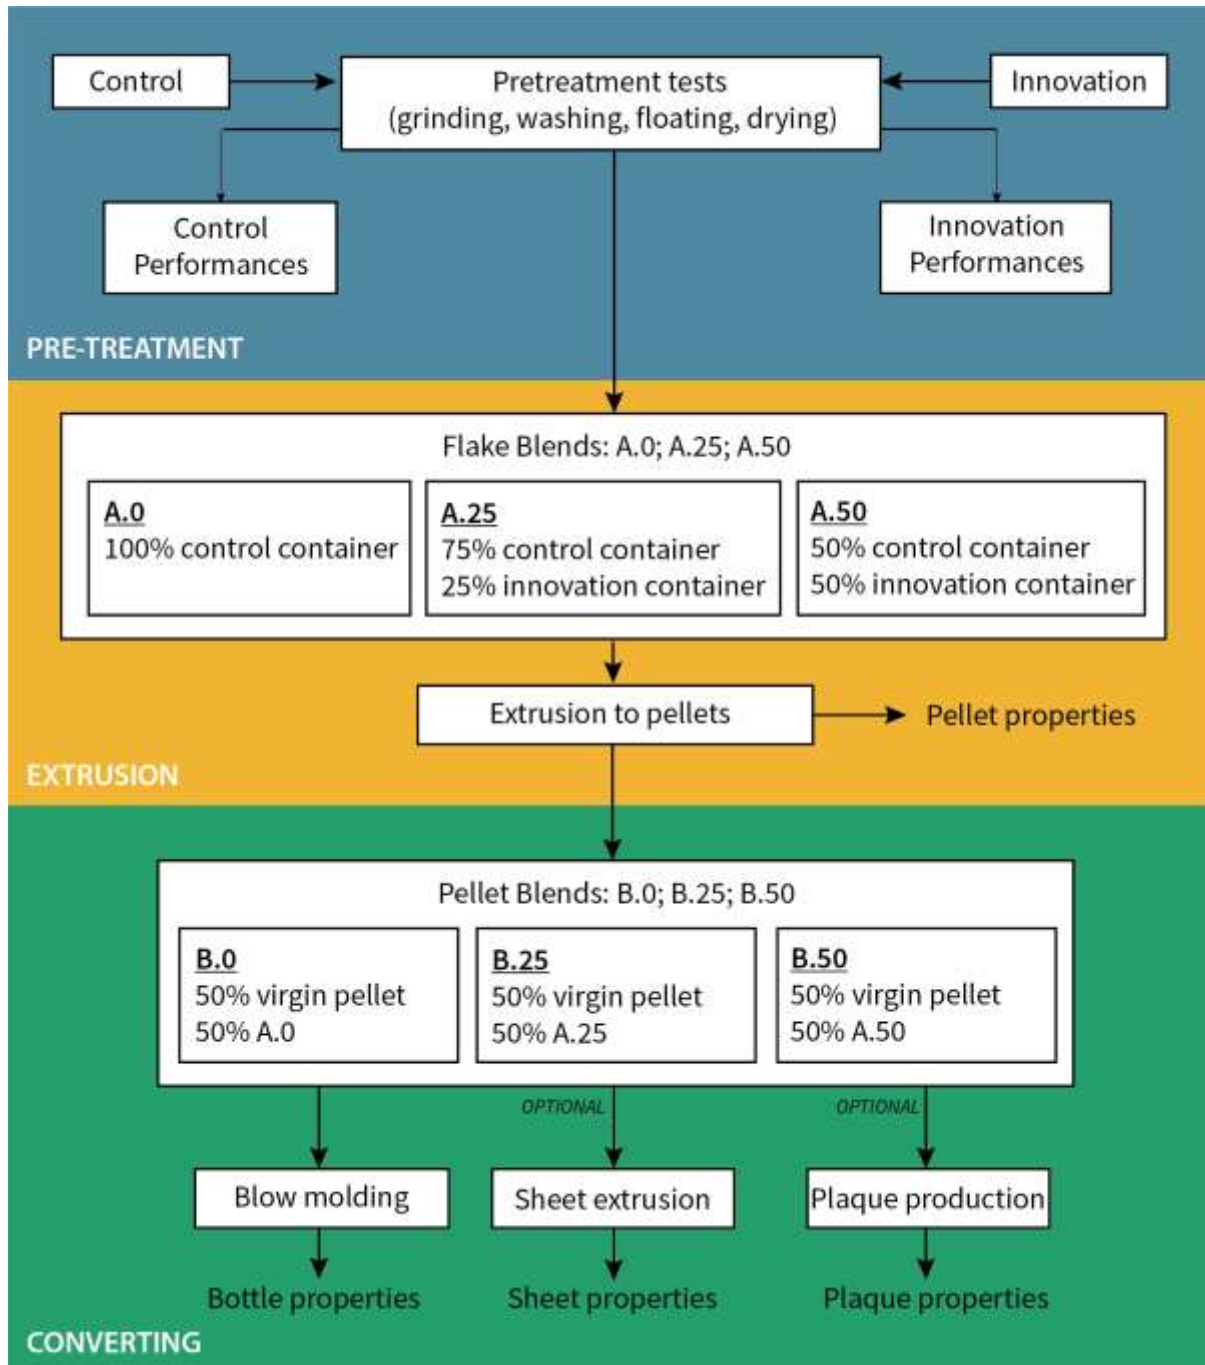

The methodology described above shall be followed precisely and any modifications or problems must be noted during the testing phase.

An Evaluation Report compiling all the results obtained shall be prepared by the lab to report to the RecyClass HDPE Technical Committee which will interpret the results. Any remarks during following the Protocol shall be also noted down.

## **4.1. CONTROL SELECTION**

The control HDPE for use following the Protocol can be selected by:

- **Option 1:** If there is a HDPE container on the market, similar to the innovation and is known to be recyclable, it can be selected as the control for this Protocol, with/upon the approval of the RecyClass HDPE TC.
- **Option 2:** If there is an HDPE container known to be recyclable, consisting of the same base HDPE virgin materials as the Innovation, except/apart from the specific ingredient/feature being evaluated, it can be selected as the control for this Protocol, with the approval of the RecyClass HDPE TC.
- **Option 3:** The Applicant can select a HDPE resin with the same critical technical specifications for MFI and density as the innovation article,  $\pm 0.02$  MFI and  $\pm 0.005$  density can be used as the control for this Protocol, with/upon the approval of RecyClass HDPE TC.

These options are to be used to make both the control flakes and the blends with innovation container flakes that will contain the additive, coating, label, adhesive or multilayer resin for the recycle study.

A selection of control samples to be used is reported in Annex I.

For the purpose of the tests the Applicant should provide at least 10 kg amount of innovation material (as packaging) and 25 kg amount of control material (as packaging) which allows for blend preparations of 5 kg each. More innovation material could be requested if optional tests are required by the RecyClass HDPE Technical Committee. It is worth pointing out that the innovation to be tested is not limited to the main body of the packaging but to all its parts. Therefore, the innovation has to be submitted to the laboratory procedures with labels, adhesives, closure system, liners, seals, valves. If it can be correctly argued that labels and adhesives have no impact on the innovation, the innovation samples can be processed without the presence of labels and adhesives.

## **4.2. PRE-TREATMENT**

### **4.2.1. GRINDING**

Control and innovation HDPE containers are separately grinded in order to fit the throat of a standard laboratory extruder.

#### **Procedure:**

- Grind separately control and innovation samples to flakes of 3 to 15 mm.
- Store in separate containers.



#### 4.2.2. AIR ELUTRIATION

Control and innovation HDPE flakes are separately elutriated with air to remove light fraction.

**Procedure:**

- Elutriate with air with one pass and with less than 2% loss set for the control flakes. More innovation failures may occur if this step is omitted.

#### 4.2.3. WASHING

At the state of the art, European HDPE recycling lines typically use mild washing conditions, no detergents nor strong chemicals (Procedure 1). However, in few recycling lines the washing is operated with more aggressive conditions (Procedure 2) aiming to a following food contact bottle-making process. The RecyClass HDPE Technical Committee and the Applicant are requested to select a washing procedure based upon the intended end-use application. Both the procedures take care of labels, adhesives, coatings, and printing present in the innovation HDPE container.

The following procedures have to be utilized for both control and innovation samples, separately.

**Procedure 1:**

- Prepare the wash in a vessel at a 1:4 ratio (5 kg flakes vs 20 l water) with tap water. No added detergents or caustic soda.
- Heat the wash at 40°C.
- Wash each sample separately at a 1:4 ratio (5 kg flakes vs 20l water) at 1.000 rpm for 5 minutes.
- Rinse the flakes in the strainer with cold running tap water and stir vigorously for 5 minutes using manual stirring bar. Then drain the material.

**Procedure 2 (optional):**

- Prepare the wash solution in a vessel at a 1:4 ratio (5 kg of flakes vs 20 l water + 0.3%w Triton X-100 and 1% caustic soda (NaOH)). Triton X-100 must be dissolved in cold water before the addition of caustic soda.
- Heat the solution at 90°C on a plate covering the vessel to minimize evaporation.
- Overhead stirrer at 1000 rpm, 2.5 cm above the bottom.
- With stirrer on add HDPE flakes with its components to the solution (maintain a 1:4 ratio, i.e. 1 part of flake for 4 parts of water).
- Readjust stirrer to 1000 rpm and continue agitation for 5 minutes at 90°C.
- Turn off and remove the stirrer. Remove the vessel from heat plate and immediately strain the solution with test components and flakes.
- Rinse the flakes in the strainer with cold running tap water and stir vigorously for 5 minutes using manual stirring bar. Then drain the material. Save the water for further inspection.
- Spread flakes on a sheet and dry it an oven at 60°C to release surface moisture to less than 1%. Separate flakes and remaining components if required. Washed and unwashed flakes will be compared for visual (and instrumental, if required) evaluations.

#### 4.2.4. FLOATATION

Following the washing, the flotation process allows flake separation by density as occurring in the float/sink tank used in an industrial recycling line. For a suitable recycling, packaging design with combinations of polyethylene and other materials that sink in water should be avoided. Non-PE components floating together with HDPE flakes cannot be further separated and are extruded with HDPE. This poses relevant concerns both in the process operations and in the quality of the recyclate, undermining its applications such as containers, pipes and sheets.

The following procedure has to be utilized for both control and innovation samples, separately.

##### **Procedure**

- Fill a vessel with tap water at a 1:6 ratio (5 kg washed flakes vs 30 l water).
- Put each sample separately in the water and stir at 500 rpm for 2 minutes.
- Stop the stirrer and allow the water to rest for 2 minutes.
- Remove all the materials that float at the surface with a sieve.
- Take photos of the floating and sinking fractions separately
- Save the wash for visual evaluation

The efficiency of the sink/float separation should be measured using 50 g of washed flakes of innovative samples and a graduated beaker filled with tap water, as described by the following procedure. Repeat the procedure for washed and dried innovation flakes, with and without caps and labels.

##### **Procedure**

- Fill a 1 l graduated beaker with 700 ml of tap water (pH between 7 and 8).
- Boil the water for 10 minutes, and then cool at room temperature.
- Transfer 300 ml of water in a graduated beaker
- Put the innovative sample in the water and stir at 500 rpm for 2 minutes.
- Stop the magnetic stirrer and allow the water to rest for 2 minutes.
- Take photo of the beaker.
- Remove all particles that float at the surface with a sieve.
- Take photos of the floating and sinking fractions separately.
- Save the wash for visual evaluation.
- Dry the floating fraction for 1 hour at 80 °C in a bed desiccant or 3 hours at 65 °C with air.
- Cool to room temperature, weigh and record the weight of the float fraction.
- Repeat the procedure with 50 g of the innovation flakes without caps and labels (if any).
- Calculate the test efficiency as  $(\text{weight of sinking fraction}) / (\text{weight of innovative sample}) \times 100$  (in %), separately for the innovation samples with and without caps and labels

#### 4.2.5. DRYING

Reduce the flake moisture with ambient air to release surface moisture to less than 1%.

**Procedure:**

- Dry the flakes collected after floatation with air at room temperature for 24 h, without the application of vacuum or heat sources.

**4.2.6. AIR ELUTRIATION**

Control and innovation HDPE flakes are separately elutriated with air to remove light fraction.

**Procedure:**

- As for the second step, elutriate flakes with air with one pass and with less than 2% loss set for the control flakes.

**5. EXTRUSION****5.1. FLAKE BLENDS PREPARATION**

For each sample obtained, to evaluate and record the properties of innovation HDPE container against control as laid out in this Protocol, a set of flake blends is prepared as described in Table 1. Blends shall be produced once the control and innovation containers have separately gone through all pre-treatment steps described below.

Keep separated the control and innovation flakes obtained following the previous steps, and air dry for 24 h at ambient air. Then, according to the values reported in Table 1 prepare three different blends with 100% control (and 0% innovation), 75% control - 25% innovation, and 50% control - 50% innovation, and tag them respectively as A.0, A.25 and A.50.

For the purpose of the tests the Applicant should provide enough innovation and control materials which allows for the blend preparations. The laboratory carrying out the Protocol testing can define the amounts according to their best knowledge.

**5.2. FLAKE BLENDS COMPOSITION**

Three different blends with 0%, 25% and 50% of innovation HDPE container, will be prepared as described in Table 1.

*Table 1: Flake blends composition to produce pellets*

<b>Blend</b>	<b>Composition</b>	<b>% Control</b>	<b>% Innovation</b>
<b>A.0</b>	100% Control	100	0
<b>A.25</b>	75% Control 25% Innovation	75	25

<b>A.50</b>	50% Control 50% Innovation	50	50
-------------	-------------------------------	----	----

### 5.3. PELLET PRODUCTION

Both control and innovation flakes can be mixed manually before extrusion for blends preparation. The flakes will be dried at the same conditions with a desiccant bed drying unit or with hot air and extruded at temperatures of 220 °C. The extrudate will be melt filtered (about 120 microns filtration). Control flake sample A.0 has to be extruded first. Further size reduction before extrusion is acceptable if needed to allow good feeding of the material into the extruder. See additional information in Table 2.

Table 2: Pellet production purpose & overview

Flake Compositions	Kg of blend required	Purpose of blend
A.0 100% Control flake	Per lab requirement for a 30-minute run time	All tests compared to control values
A.25 75% Control with 25% innovation	Per lab requirement for a 30-minute run time	Required for information on the impact of concentration of the innovation on recycling (comparison to control values)
A.50 50% Control with 50% innovation	Per lab requirement for a 30-minute run time	Required for comparison to control values

#### Procedure:

- Dry samples A.0, A.25 and A.50 with a bed desiccant for 1 hour at 80 °C or with hot air at 65 °C for 3 hours.
- Extrude for first the sample A.0 (the control blend) at a temperature of 220 °C and with a 120 µm melt filter pack, for no less than 30 minutes.
- Monitor the extrusion process for heat stability.
- Rapidly cool the extrudate in a water bath and fed into a pelletizer.
- The pelletizer speed has to be controlled to get a final pellet with a diameter of 3 mm.
- Monitor pressure build-up during pelletizing and report significant differences.
- Randomly collect the pellets to perform all the characterizations reported in Table 3.
- Change the melt filter pack between samples for visual examination.
- Be sure to produce enough pellets for all the tests, including the conversion tests.

Record properties' results in Table 3. The processing conditions used for all the samples must be identical. If some operating conditions have to be modified for A.25 and A.50 samples, this information must be documented in the report. A small amount of each sample (50 g) will be retained for RecyClass Technical Committee and the Applicant. The extruded pellets will be tested for pellet properties evaluation (Table 3). The pellets of the test samples will be compared with the pellets of the control sample. All pellets should meet the requirements reported in the Table 3.

If filterability is seen as a potential problem for the innovative samples, a dedicated filter test should be requested by the RecyClass HDPE Technical Committee.

### *5.3.1. FILTRATION TEST (OPTIONAL)*

Filter contamination problems may occur when one of the components in the innovation sample is causing gels, larger particles, or releases degraded particles. Pressure drop has to be monitored during pelletizing since a pressure increase is an indication of the risk of filter contamination. If from previous step, the monitoring of pressure-drop and the visual inspection of the filter after the pelletization induce to further analyze contamination, a dedicated filtration test should be done. To limit the test duration, the innovation sample will not be mixed with control HDPE.

About 5 kg of pellets from the pure control HDPE and the pure innovation HDPE samples will be separately extruded for a minimum of 30 minutes and filtered using a 120 microns screen pack. The 100% control sample has to be extruded for first.

#### **Procedure:**

- Dry the control sample before to be extruded with a bed desiccant for 1 hour at 80 °C or with hot air at 65 °C for 3 hours.
- Extrude the sample at a temperature of 220 °C and with a 120 µm melt filter pack, for no less than 30 minutes.
- If required, small changes in the process parameters are admitted keeping the extrusion stable over the time but have to be recorded. However, continuous adjustments of the operating parameters during the runs to overcome steady-state conditions are not admitted.
- Monitor the pressure drop during the test and register variations.
- Repeat the procedure for the innovation sample with the identical operating parameters used for the control sample filtration.

The test is passed if the pressure before the filter doesn't double respect to the start pressure during or at the end of the run.

### 5.3.2. PELLET PROPERTIES EVALUATION

Table 3: Pellet properties evaluation

Assessment	Result	Standard	Benchmark Recommendation
Bulk Density (kg/m <sup>3</sup> )		Annex B of EN 15344	No less than 550 kg/m <sup>3</sup>
Density (kg/m <sup>3</sup> )		ISO 1183-1	±0,01 g/cm <sup>3</sup> for A.25 and A.50 respect to the control sample. Moreover A.50 lower than 0.995 g/cm <sup>3</sup>
Melt Index (g/10 min)		ISO 1133 (190 °C/2.16kg)	Between 0.2 and 0.9 g/10min
Ash content (%)		ISO 3451-1 by TGA	A.50 lower than 2%
Filtration (µm)		Visual inspection	No build-up on screen
Moisture (% weight)		Moisture analyzer	Record
Differential Scanning Calorimetry (°C)		ISO 11357-3	Melting point 130-140 °C
Impurities		Visual inspection	Record
Surface appearance		Visual inspection	Record
Volatiles (%)		10 g air-dried pellets exposed to 160°C for 10 minutes	±0.1% for A.25 and A.50 respect to A.0
PP (%)		Differential Scanning Calorimetry or Spectroscopic measurement	No more than 2% for A.25 and A.50.
Delta Pressure (MPa)		Measure it after extruding through 120 microns for the stable 30 minutes run time	No more than 10% higher pressure respect to the control sample

## 6. CONVERSION

Based on the obtained results, the RecyClass HDPE Technical Committee will decide if the innovation presents some critical properties. On that basis, the Technical Committee reserves the right to further test the innovation. Otherwise, if the results are aligned with HDPE recyclate specimens the Technical Committee and the Applicant will define the way to further test the innovation on the base of the main applications available on the market.

Since the Protocol aims to assess the highest-value recyclate application, blow molding will be a priority. However, the RecyClass HDPE Technical Committee according with the Applicant could decide to test the innovation for sheet extrusion or for plaques production.

In any case, three blends of innovation and control pellets will be produced aiming to assess different innovation concentration in the recycling stream, as following reported.

### 6.1. PELLET BLENDS COMPOSITION

Once HDPE pellets have been produced and tested, three additional blends of at 50% virgin – 50% blend A shall be produced for application tests. Keep separated the pellet samples previously produced and dry it for 10 minutes at 60°C. Then according to the values reported in following Table 4 prepare three different blends with 0% innovation (50% virgin and 50% A.0 pellets), 12.5% innovation (50% virgin and 50% A.25 pellets), and 25% innovation (50% virgin and 50% A.50 pellets), and tag them as samples B.0, B.25 and B.50 respectively.

Pellet blends will be composed of 0%, 12.5% and 25% by weight of the innovation HDPE container.

*Table 4: Pellet blends composition for application tests*

<b>Blend</b>	<b>Composition</b>	<b>% Control</b>	<b>Effective % Control</b>	<b>Effective % Innovation</b>
<b>B.0</b>	50% Virgin 50% A.0	50	50	0
<b>B.25</b>	50% Virgin 50% A.25	50	37.5	12.5
<b>B.50</b>	50% Virgin 50% A.50	50	25	25

### 6.2. BOTTLES PRODUCTION

The Applicant has to submit its innovation primarily to blow molding to test the recyclate obtained by the innovation in a closed-loop application, i.e. a bottle-to-bottle process.

Control blend B.0 has to be molded first.

Table 5: Bottle production purpose & overview

<b>Pellet blends Compositions</b>	<b>Kg of blend required</b>	<b>Purpose of blend</b>
<b>B.0</b> 50% Virgin 50% A.0 pellets	Per lab requirement for a 30-minute run time	All tests compared to control values
<b>B.25</b> 50% Virgin 50% A.25 pellets	Per lab requirement for a 30-minute run time	Required for information on the impact of concentration of the innovation on recycling (comparison to control values)
<b>B.50</b> 50% Virgin 50% A.50 pellets	Per lab requirement for a 30-minute run time	Required for comparison to control values

**Procedure:**

- The samples B.0, B.25 and B.50 should be blow molded at 170-180 °C into one liter straight-wall generic base monolayer motor oil bottle, 1 mm tick.
- The cross section can be rectangular or square.
- The bottom corners should have radii as small as commercial motor oil bottles.
- Bottle height should be typically for one liter motor oil bottles.
- Neck may be offset.
- The bottle must weigh  $50 \pm 5$  grams.
- Samples B.25 and B.50 have to be blown following the identical operating conditions of the control sample B.0.
- Small variations in operating conditions could be acceptable but have to be documented in the report.
- Record properties' results in Table 6. If some operating conditions have to be modified for B.25 and B.50 samples, this information must be documented in the report.

**6.2.1. BOTTLE PROPERTIES EVALUATION**

Table 6: Bottle properties evaluation

<b>Assessment</b>	<b>Result</b>	<b>Standard</b>	<b>Benchmark Recommendation</b>
Bottle Appearance		Visual defects including surface roughness	Minimum for 10 bottles (compare with B.0)
Bottle Integrity		Visual inspections	Minimum for 10 bottles (compare with B.0)



Bottle Dimension		Height	±5% respect to B.0
Bottle Weight		Weight	±5% respect to B.0
Bottle Capacity		Brimful	±5% respect to B.0
Thickness		Top, mid and bottom side wall, shoulder, base corner	Minimum 0.3 mm for each measure
Top load		ASTM D2659 (no ISO available)	< 5% decrease respect to B.0
Drop impact		ASTM D2463, procedure B (no ISO available)	No less than 95% mean failure height respect to B.0
Additional observation		Deposit on tooling	None observed respect to B.0 for 2 hours bottle production

### 6.2.2. TENSILE PROPERTIES TESTING

Tensile properties have to be tested for bottle application to minimize the influence of a subsequent processing and obtain a more realistic comparison.

Table 7: Bottle tensile properties evaluation

Assessment	Result	Standard	Benchmark Recommendation
Stress at Yield (MPa)		ISO 527-2	Compare B.25 and B.50 with B.0
Stress at Break (MPa)		ISO 527-2	Compare B.25 and B.50 with B.0
Elongation at Break (%)		ISO 527-2	Compare B.25 and B.50 with B.0
Elongation at Yield (%)		ISO 527-2	Compare B.25 and B.50 with B.0
Strength (MPa)		ISO 527-2	Compare B.25 and B.50 with B.0
Elongation at Strength (%)		ISO 527-2	Compare B.25 and B.50 with B.0

### 6.3. SHEETS PRODUCTION (OPTIONAL)

On the base of results obtained by pellet characterization, the RecyClass HDPE Technical Committee and the Applicant can optionally decide to test the innovation for sheet extrusion.

As reported in the section 5.1, prepare three different blends with 0% innovation (50% virgin and 50% A.0 pellets), 12.5% innovation (50% virgin and 50% A.25 pellets), and 25% innovation (50% virgin and 50% A.50 pellets). Tag them as C.0, C.25 and C.50, respectively.

Control pellet blend C.0 has to be extruded first. See more information in Table 8.

Table 8: Sheet production process & overview

Pellet Compositions	Kg of blend required	Purpose of blend
<b>C.0</b> 50% Virgin 50% A.0 pellets	Per lab requirement for a 30-minute run time	All tests compared to control values
<b>C.25</b> 50% Virgin 50% A.25 pellets	Per lab requirement for a 30-minute run time	Required for information on the impact of concentration of the innovation on recycling (comparison to control values)
<b>C.50</b> 50% Virgin 50% A.50 pellets	Per lab requirement for a 30-minute run time	Required for comparison to control values

**Procedure:**

- Dry samples C.0, C.25 and C.50 at 60°C for 10 minutes.
- Extrude sheets with thickness of 800 µm under conditions determined for the control sample C.0.
- Extrusion run time per variable, no less than 30 minutes.
- Samples C.25 and C.50 have to be extruded following the identical operating conditions of the control sample C.0.
- Small variations in operating conditions could be acceptable but have to be documented in the report.

Record properties' results in Table 9. If some operating conditions have to be modified for C.25 and C.50 samples, this information must be documented in the report.

**6.3.1. SHEET PROPERTIES EVALUATION**

Table 9: Sheet properties evaluation

Assessment	Result	Standard	Benchmark Recommendation
Flexural modulus		ISO 178	Minimum 600 N/mm <sup>2</sup>
Tensile Strength at Yield		ISO 527	Minimum 18 N/mm <sup>2</sup>
Colour		Visual inspection	No discolouration
Surface Appearance		Visual inspection	No black specks

Inclusions of extraneous material		Visual inspection	Record
-----------------------------------	--	-------------------	--------

#### 6.4. PLAQUES PRODUCTION (OPTIONAL)

On the base of results obtained by pellet characterization, the RecyClass HDPE Technical Committee and the Applicant can optionally decide to test the innovation for plaques production. According to the values reported in the following Table prepare three different blends with 0% innovation (50% virgin and 50% A.0 pellets), 12.5% innovation (50% virgin and 50% A.25 pellets), and 25% innovation (50% virgin and 50% A.50 pellets). Tag the blends as D.0, D.25 and D.50, respectively.

Control blend D.0 has to be molded first. See more information in Table 10.

Table 10: Plaque production purpose & overview

Pellet Compositions	Kg of blend required	Purpose of blend
<b>D.0</b> 50% Virgin 50% A.0 pellets	Per lab requirement for a 30-minute run time	All tests compared to control values
<b>D.25</b> 50% Virgin 50% A.25 pellets	Per lab requirement for a 30-minute run time	Required for information on the impact of concentration of the innovation on recycling (comparison to control values)
<b>D.50</b> 50% Virgin 50% A.50 pellets	Per lab requirement for a 30-minute run time	Required for comparison to control values

#### Procedure:

- Preheat the hot press to 175°C.
- Weigh and add pellet samples to the mold cavity.
- Close the mold and put the mold on the hot press for 10 minutes to allow the sample preheating.
- After 10 minutes apply fluidly force to the mold from 0 to 4,500 kg in 15 seconds and then maintain that force for 1 minute.
- Release the force from the mold and remove mold from the hot press.
- Air cool the mold at ambient air until it become warm to the touch.
- Run time per variable, no less than 30 minutes
- Samples D.25 and D.50 have to be processed following the identical operating conditions of the control sample D.0.

- Small variations in operating conditions could be acceptable but have to be documented in the report.

Record properties' results in Table 11. If some operating conditions have to be modified for D.25 and D.50 samples, this information must be documented in the report.

#### 6.4.1. PLAQUE PROPERTIES EVALUATION

*Table 11: Plaque properties evaluation*

<b>Assessment</b>	<b>Result</b>	<b>Standard</b>	<b>Benchmark Recommendation</b>
Flexural modulus		ISO 178	Minimum 600 N/mm <sup>2</sup>
Tensile Strength at Yield		ISO 527	Minimum 18 N/mm <sup>2</sup>
Color		Visual inspection	No discoloration
Surface Appearance		Visual inspection	No black specks
Inclusions of extraneous material		Visual inspection	Record

## ANNEX I - CONTROL SAMPLES SELECTION

HDPE	density, g/cm <sup>3</sup>	MFI, g/10min (190 °C/2.16 kg)	ESCR, h
ENI Versalis Eraclene B52	0.954	0.25	> 60
INEOS Rigidex® HD5502S	0.954	0.20	6
INEOS Rigidex® HD5802BM	0.958	0.30	> 200
LYONDELLBASELL Hostalen GF4750	0.950	0.40	high
REPSOL Alcudia® 5503	0.955	0.25	100